

Ceramic raw materials from the State of Maranhão, Brazil. Part 1: chemical and mineralogical characterization and technological properties of clays from São Luís, Rosário, Pinheiro and Mirinzal

José Manuel Rivas Mercury

Engenheiro Químico, Doutor em Físico-Química Inorgânica, Professor do Programa de Pós-Graduação em Engenharia dos Materiais (PPGEM), Departamento de Química (DAQ) - Instituto Federal do Maranhão (IFMA)
rivascefema@gmail.com

Gricirene Sousa Correia

Engenheiro Mecânico, M.Sc. em Engenharia dos Materiais (PPGEM/IFMA), Departamento de Mecânica e Materiais (DMM) - IFMA
gricirene@gmail.com

Nazaré Socorro Lemos Silva Vasconcelos

Química Industrial, Doutora em Química pela Universidade Estadual Paulista Júlio de Mesquita Filho, Professora do Programa de Pós-Graduação em Engenharia dos Materiais (PPGEM), Departamento de Química (DAQ) - Instituto Federal do Maranhão (IFMA)
ndsocorro@ifma.edu.br

Aluísio Alves Cabral Jr.

Licenciado em Física, Doutor em Engenharia de Materiais, Professor do Programa de Pós-graduação em Engenharia dos Materiais (PPGEM), Departamento de Física (DCE) - Instituto Federal do Maranhão (IFMA)
acabraljr@ifma.edu.br

Rômulo Simões Angélica

Geólogo, Doutor em Mineralogia e Geoquímica, Professor do Programa de Pós-Graduação em Geologia e Geoquímica Instituto de Geociências da UFPA
angelica@ufpa.br

Matérias-primas cerâmicas do Estado do Maranhão. Parte 1: caracterização químico-mineralógica e propriedades tecnológicas de argilas dos municípios de São Luís, Rosário, Pinheiro e Mirinzal

Resumo

Nesse trabalho, foram caracterizadas algumas argilas coletadas nos municípios de São Luís, Rosário, Pinheiro e Mirinzal. A caracterização foi realizada através dos ensaios de difração de raios X, massa específica real, capacidade de troca de cátions (CTC), área superficial, distribuição granulométrica, análise química, análise térmica (TG-DTA) e limites de Atterberg. Ensaios tecnológicos de retração linear, antes e após a queima, absorção de água e tensão de ruptura a flexão, em três pontos, foram realizados em corpos de prova prensados uniaxialmente a 20 MPa e tratados termicamente em 850, 950, 1050, 1150 e 1250°C. Os resultados obtidos permitiram identificar duas argilas de queima branca, constituídas de quartzo, caolim, feldspato e anatásio, com excelentes propriedades para uso em cerâmica branca. As restantes são queima vermelha e possuem composição mineralógica de quartzo, caolim, feldspato, montmorilonita, hematita e goetita. Estas últimas apresentaram valores moderados de plasticidade e são adequadas para aplicações em cerâmica vermelha.

Palavras-chave: Matérias-primas cerâmicas, Maranhão, caracterização.

Abstract

This work involved the characterization of clays collected in the municipalities of São Luís, Rosário, Pinheiro and Mirinzal (state of Maranhão, Brazil), based on specific mass, specific surface area, cation exchange capacity (CEC), particle size distribution, X-ray diffraction (XRD), differential thermal analysis (DTA), thermogravimetric analysis (TG-DTA) and Atterberg limits. Technological tests for ceramic applications

were also carried out on compacts pressed under 20 MPa and heat-treated at 850, 950, 1050, 1150 and 1250°C. Our results indicated that two of the clays composed of kaolinite, quartz, and anatase with high plasticity limits, have excellent properties and can be used in the whiteware industry. The other ones are red-firing clays and have a mineralogical composition of quartz, kaolin, feldspar, montmorillonite, hematite and goethite. The latter showed low and moderate values of plasticity, which makes them suitable for the production of heavy clay products.

Keywords: Raw materials, Maranhão, Characterization.

1. Introduction

The state of Maranhão today has more than 120 companies operating in the red ceramics sector. Most of these companies are situated in 15 microregions, which manufacture approximately 22 million bricks and 18 million roof tiles per month, generating over 5,000 direct jobs (IBGE, 2007; ABC, 2002; Santana et al., 2008). However, the raw materials used in many of these regions do not undergo a beneficiation process or proper

characterization, which contributes to lower the quality levels of the manufactured products.

Despite the importance of these companies to the state's economy, the literature contains no data on the occurrence of ceramic raw materials, or scientific and technological studies to guide future investments of the private sector in this region (Mello, 2011).

Therefore, the purpose of this pioneering work was to characterize four clays collected in the municipalities of São Luis, Rosário, Pinheiro and Mirinzal, based on their chemical, mineralogical and technological properties. These materials are widely used in the manufacture of traditional ceramic materials. From our point of view, this paper contributes to the knowledge about the ceramic raw materials of Maranhão.

2. Materials and methods

Materials

The raw clays collected in the municipalities of São Luis, Rosário, Pinheiro and Mirinzal, situated 67, 86 and 154 km from São Luis, respectively, will hereinafter be identified as ASL (São Luis Clay), ARO (Rosário

Clay), AP (Pinheiro Clay) and AM (Mirinzal Clay). The materials were sun-dried to obtain constant moisture content. Then they were cleaned (Souza Santos, 1987) and disagglomerated in an electric mortar mixer. Next, some

aliquots were removed for granulometric testing. After quartering the rest of the materials (3 kg), they were ground and sifted through a sieve (150 µm mesh) to obtain a powder suitable for the remaining tests.

Methods

The samples were analyzed chemically by different methods: gravimetry, to determine the total SiO₂ and the loss on ignition (LOI); complexometry (EDTA) to measure the total Al₂O₃; and colorimetry to estimate the total Fe₂O₃ and TiO₂. The CaO, MgO, Na₂O and K₂O contents were analyzed by atomic absorption spectrometry (AAS) after alkali fusion.

The thermal behavior of the clays was examined by thermogravimetric analysis (TGA) and differential thermal analysis (DTA), using Al₂O₃ crucibles and an oxidizing atmosphere up to 1100°C at a heating rate of 10°C/min, in a PL Thermal Sciences thermal analyzer equipped with an STA 1000/150 simultaneous thermal analyzer (Stanton Redcroft Ltd.).

To determine the total fraction of the mineral phases (powder), the samples were analyzed in a back-loading sample holder to avoid orientation of the aggregates. The samples' clay fraction (< 2µm fraction) was separated by sedimentation

after dispersion with NH₄OH 0.1 mol L⁻¹, using the slide orientation technique. In addition, they were air-dried, solvated with ethylene glycol for 24h and heat-treated at 500°C/2h.

The XRD spectra of the total fraction were recorded with an X'Pert PRO diffractometer (PANalytical PW3040/60), equipped with a PW3050/60 goniometer (Theta/Theta) and a ceramic X-ray tube with Cu anode (CuKα₁ = 1.5406 Å), operating with 40 mA current, 40 kV voltage, with a step size of 0.02° (2θ), a count time of 5 s, at an angular range of 5-70° (2θ). The diffractograms of fine fraction (< 2 µm) were recorded with the Co anode (CoKα₁ = 1.78901 Å) to prevent efflorescence of iron in the angular region of 3-34° (2θ) with a step size of 0.02° (2θ) and a counting time of 10 s. The mineral phases were indexed using the PDF-ICDD database (Powder Diffraction File – International Center for Diffraction Data).

The semiquantitative analysis of the

crystalline phases was carried out based on the XRD results of the total fraction and the fine fraction with non-oriented aggregates, and on a chemical analysis (Coelho et al., 2002; Johnson et al., 1985; Loubser and Verryin, 2008) by X-ray fluorescence (XRF).

The physical characterization of the samples involved the following experiments: Granulometric distribution according to the Brazilian Association of Technical Standards – ABNT standard NBR 7181 (ABNT, 1984); cation exchange capacity and surface area by the methylene blue saturation method (Ferreira, 1972); Atterberg limits: Plasticity Index (PI), Liquid Limit (LL) and Plasticity Limit (PL), according to the Brazilian NBR 6454 (ABNT, 1984), and NBR 7180 standards (ABNT, 1984); and Real Specific Mass and Water Absorption (WA) according to the NBR 6220 standard (ABNT, 1997).

Rectangular test specimens with dimensions of 8 x 2.0 x 0.5 cm, with

moisture content of 8% in weight, were compacted uniaxially under a pressure of 20 MPa and dried at 110°C for 24h. The compacts were heat-treated at 850, 950, 1050, 1150 and 1250°C in an electric furnace (Nabertherm

GmbH, Germany) in an oxidizing atmosphere, applying a heating rate of 5°C/min with a dwell time of 3 hours. After the heat treatment, the following ceramic properties were determined: linear shrinkage (S_L), water absorption

(WA) and flexural stress rupture (FSR) under three-point bending (TIRA Test 2705), as recommended by the Brazilian ABNT standards NBR-6113/97 (ABNT, 1984b) and NBR 6220/97 (ABNT, 1984b).

3. Results and discussion

Mineralogical characterization

Figure 1 (A-B) illustrates the results of the XRD analysis of the total fraction of the AM, AP, ARO and ASL clays.

In Figure 1A, note that the AM and AP samples present a similar mineralogical composition, both showing the presence of the following minerals: quartz (26.64° (2 θ); d = 3.34 Å (101)); kaolinite (12.30° (2 θ); d = 7.10 Å (001); 19.83° (2 θ); d = 4.41 Å (110); and 24.98° (2 θ); d = 3.56 Å (002)); and anatase (25.28° (2 θ); d = 3.52 Å; (001)). Neither

of these samples (AM and AP) showed reflections corresponding to the mineral iron. In contrast, the ARO and ASL samples (Figure 1B) show the minerals quartz, kaolinite, anatase, illite (8.27° (2 θ); d = 10.00 Å (001)), feldspar (27.48° (2 θ); d = 3.25 Å) and minor contents of goethite (21.5 ° (2 θ); d = 4.18 Å (101)) and hematite.

A more in-depth study of the mineralogy of the clays based on an analysis of the clay fraction (< 2 μ m) by the oriented

aggregation (OA) method indicated that the AM and AP clays are constituted primarily of the clay mineral kaolinite (Figure 2). In Figure 2A, note that the glycosylated OA of the ARO sample, after heat treatment at 500°C/2h, shows reflections typical of kaolinite and illite (10.22°(2 θ); d = 10.01 Å; 20.66°(2 θ); d = 4.98 Å) of low intensity.

On the other hand, the diffractogram of the ASL sample (Figure 2B) presents reflections of low intensity of

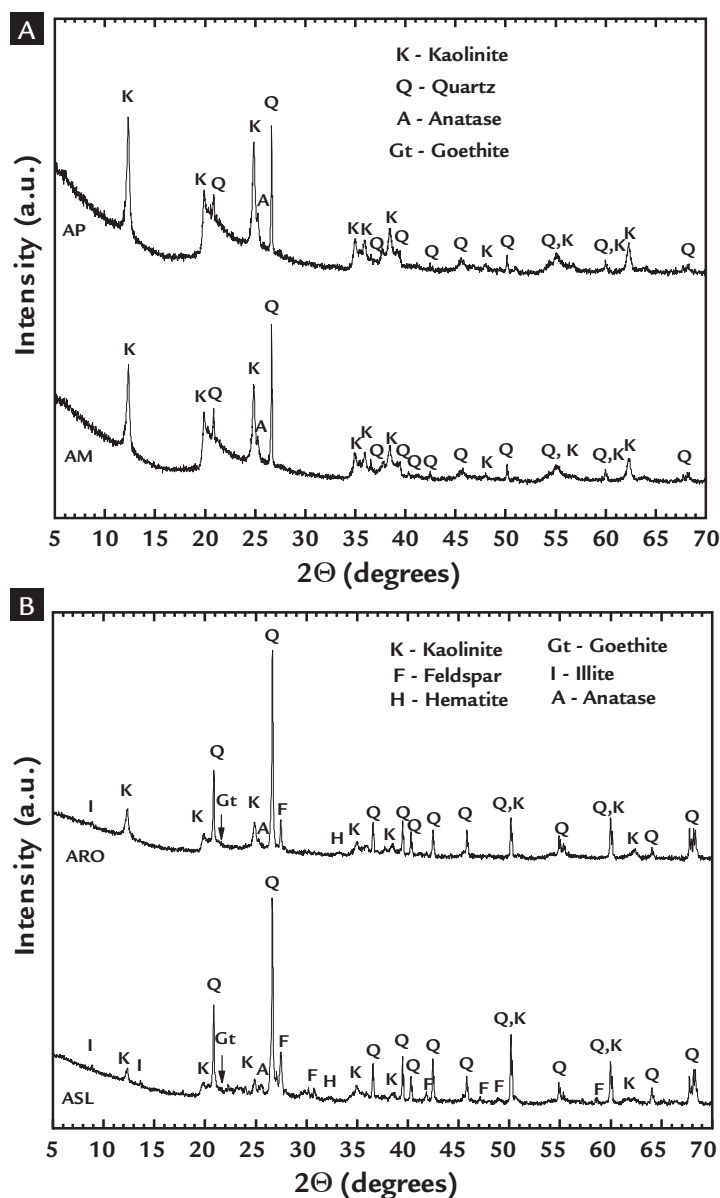


Figure 1
Diffractograms of the
total clay fraction of:
A) AM and AP.
B) ARO and ASL clays.

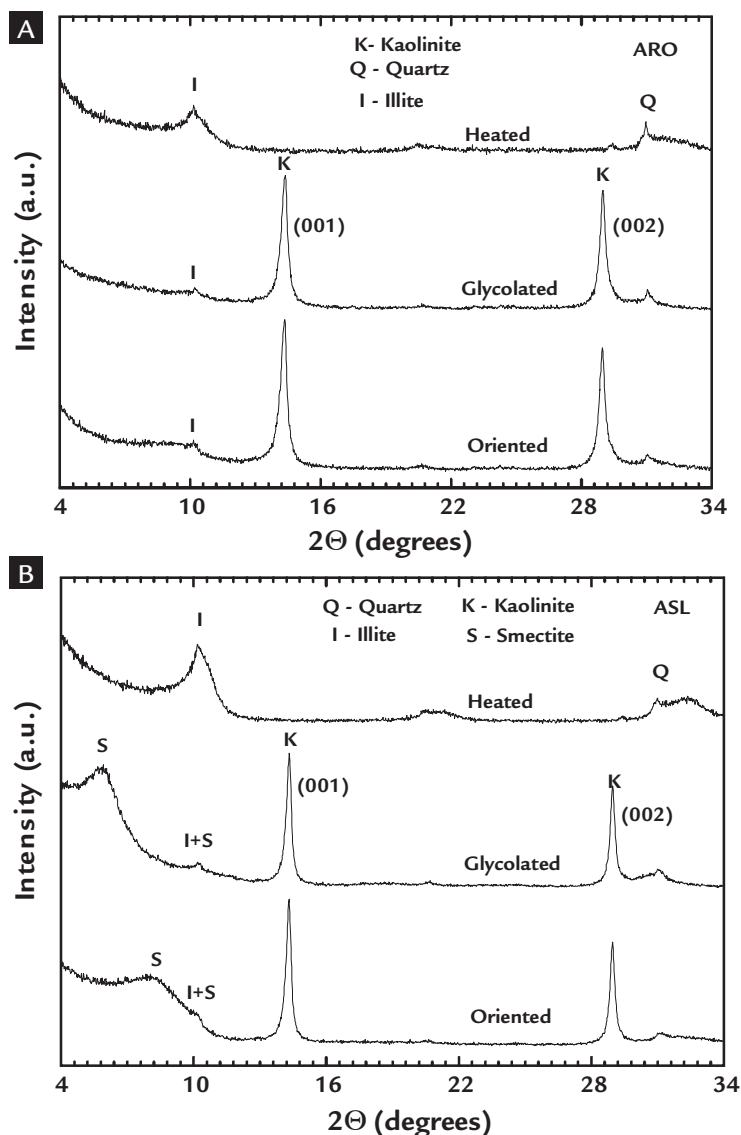


Figure 2
 Diffractograms of the clay fraction of samples:
 A) ARO.
 B) ASL, in the form of oriented aggregates (oriented), solvated with ethylene glycol (glycolated) and treated at 500°C/2h (heated).

illite/smectite ($10.22^\circ(2\theta)$; $d = 10.01 \text{ \AA}$; $20.66^\circ(2\theta)$; $d = 4.98 \text{ \AA}$) and a band centered at $7.94^\circ 2\theta(d=12.85 \text{ \AA})$, which is shifted towards the low angle region ($5.85^\circ(2\theta)$; $d = 17.54 \text{ \AA}$). This change indicates that the interplanar distance increases in the direction of the (001) plane due to

the presence of a mineral of the smectite family (montmorillonite) (Garcia Verduch; 1985).

The presence of type 2:1 phyllosilicates deserves special attention due to their applications in other industrial areas (Souza Santos, 1992; Garcia Verduch,

1985; Vieira and Sousa Santos, 2007) and the impact of this mineral phase on the rheology of ceramic suspensions, the plasticity of pastes, and the mechanical properties of green ceramic materials after drying (Thorez, 1975; Díaz and Torrecillas, 2002).

Chemical analyses

Table 1 lists the results of the chemical analysis of the AM, AP, ARO and ASL clays. All the samples showed a high SiO_2 content (51-72%).

The concentration of Al_2O_3 in the AM and AP samples is higher than 20%, with a $\text{SiO}_2/\text{Al}_2\text{O}_3$ ratio of 1.76 and 2.45, respectively. The losses on ignition are close to the theoretical value of pure kaolinite (13.97%), suggesting the presence of kaolinite minerals and free quartz. This was confirmed in the XRD experiments, where it was observed that these clays are composed primarily of quartz and kaolinite with small amounts of

anatase. It was also found that the Fe_2O_3 contents in all the samples are lower than 3%, which suggests that these clays may present pale colors (white, cream or rose) after firing in air. Nevertheless, no mineral phase containing iron was detected by XRD, indicating that it may be present in amorphous form. Alkaline oxides ($\text{Na}_2\text{O} + \text{K}_2\text{O} < 2\%$) and alkaline earth oxides ($\text{CaO} + \text{MgO} < 1\%$) are also present in small amounts. No feldspars or carbonates were detected by XRD, which indicates that these raw materials were subjected to very strong weathering (leaching).

The ARO and ASL clays present Al_2O_3 contents of less than 20%. The $\text{SiO}_2/\text{Al}_2\text{O}_3$ ratio (3.33 and 5.23) is higher than 1.17, which indicates the presence of kaolinite minerals and free quartz in larger quantities than in the AM and AP samples. This finding is confirmed by the low values of loss on ignition (7.25 and 4.37%), the high SiO_2 contents found in the chemical analysis, and by the identification of quartz by XRD.

The Fe_2O_3 content in the ARO sample is higher than in the other samples (5%) and lower than 4% in ASL clay, which is confirmed by the

presence of goethite and hematite in both samples. Values of Fe_2O_3 above 3% indicate that both the clays should take on a reddish color after firing in air. The total alkalinity concentration ($\text{K}_2\text{O} + \text{Na}_2\text{O} < 2\%$) is low in the ARO

sample, but requires special attention in ASL clay, where it reaches values exceeding 4%. This high content of alkaline oxides promotes the formation of eutectic systems with a low melting point at 990°C and 1050°C in the

$\text{K}_2\text{O}-\text{SiO}_2-\text{Al}_2\text{O}_3$ and $\text{Na}_2\text{O}-\text{SiO}_2-\text{Al}_2\text{O}_3$ ternary systems, respectively (Levin et al., 1964; Garcia Verduch, 1985). TiO_2 does not exceed 2% in either of the samples, and the corresponding mineral detected by XRD was anatase.

Table 1
Chemical composition
of the clay samples (% in weight).

Determination (%-wt)	Samples			
	AM	AP	ARO	ASL
SiO_2	51.10	58.31	64.32	72.10
Al_2O_3	29.03	23.75	19.28	13.96
Fe_2O_3	2.85	1.80	5.27	3.75
TiO_2	2.11	1.66	1.03	0.65
P_2O_5	< 0.10	< 0.10	< 0.10	< 0.10
Na_2O	1.06	0.68	0.56	0.59
K_2O	0.26	0.12	1.27	3.88
MgO	0.47	0.26	0.44	0.38
CaO	0.12	0.05	0.02	0.05
LOI	13.00	13.15	7.71	4.54
Total	100.00	99.88	100.00	100.00
$\text{SiO}_2/\text{Al}_2\text{O}_3$	1.76	2.45	3.33	5.16

Quantification of the mineral phases

Taking into account the XRD results (AO and total fraction) and the chemical analysis of the total fraction, the mineral composition of the clays was calculated by means of normative calculation (Coelho et al., 2002; Johnson et al., 1985) (Table 2). The ideal formulas of the phases were considered, i.e., kaolinite ($\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2 \cdot 2\text{H}_2\text{O}$), quartz (SiO_2), hematite (Fe_2O_3), anatase (TiO_2), illite ($\text{K}_2\text{O} \cdot 3\text{Al}_2\text{O}_3 \cdot 6\text{SiO}_2 \cdot 2\text{H}_2\text{O}$), orthoclase ($\text{K}_2\text{O} \cdot \text{Al}_2\text{O}_3 \cdot 6\text{SiO}_2$), and albite

($\text{Na}_2\text{O} \cdot \text{Al}_2\text{O}_3 \cdot 6\text{SiO}_2$).

The quantification results confirm the XRD analysis, enabling us to state that the AM and AP clays are kaolinitic clays mixed with quartz and feldspar, while the ARO and ASL clays are mixtures of kaolinite, quartz, feldspar and illite.

Table 3 lists the real density, cation exchange capacity (CEC) and specific surface area of the samples under study. Note that the CEC of the

AM and AP clays varies from 11.77 to 12.51 meq/100g, which is compatible with that of Brazilian reference plastic clays used in ceramic whiteware (Cardoso et al., 1998; Barba et al., 1997). On the other hand, the ASL and ARO clays presented CEC values of 8.10 and 8.32 meq/100 g. The densities of all samples changed from 2.51 to 2.63 g/cm^3 and specific surface area ranging from 63.18 to 97.58 m^2/g .

Table 2
Quantification of the
mineral phases in the clays.

Mineral	Sample (%-wt)			
	AM	AP	ARO	ASL
Quartz	12.18	27.43	30.23	48.7
Kaolinite	68.30	56.91	30.07	24.2
Orthoclase	1.54	0.71	7.51	22.1
Albite	8.96	5.75	4.73	na
Mica/Illite	na*	na	19.93	1.53
Hematite/Goethite	2.85	1.80	5.27	3.0
Anatase/Rutile	2.11	1.66	1.03	na
Others	4.06	5.74	1.23	0.6
Total	100.00	100.00	100.0	100.0

* na = not available.

Table 3
Real specific mass, CEC and surface
area of the clays under study.

Determination	Sample			
	AM	AP	ASL	ARO
CEC (meq/100 g)	12.51	11.77	8.10	8.32
Specific area (MBI) (m^2/g)	97.58	91.81	63.18	64.90
Density (g/cm^3)	2.62	2.63	2.56	2.51

Thermal behavior

The thermal behavior of the clays determined by TGA and DTA is shown in Figure 3(A-B). The AM and AP clays presented a similar mass loss of 15.23 and 14.33%, which is higher than the theoretical mass loss of kaolinite (13.95%) and was attributed to hygroscopic water and organic matter in the samples. The ARO and ASL clays, in

turn, presented a continuous mass loss of 8.77 and 4.30%, respectively. The four clays showed: (i) an endothermic effect with a maximum at 72°C (AM and AP) and 65°C (ARO and ASL), which corresponds to free water loss; (ii) another endothermic event whose maximum occurred at 525°C, corresponding to the dehydroxylation

of kaolinite with the formation of metakaolinite; (iii) an exothermic reaction with maximum at about 970°C, which is attributed to the nucleation of primary mullite and/or Al:Si spinel-type phase (Souza Santos, 1987). No thermal events were detected associated with the decomposition of illite or other phases.

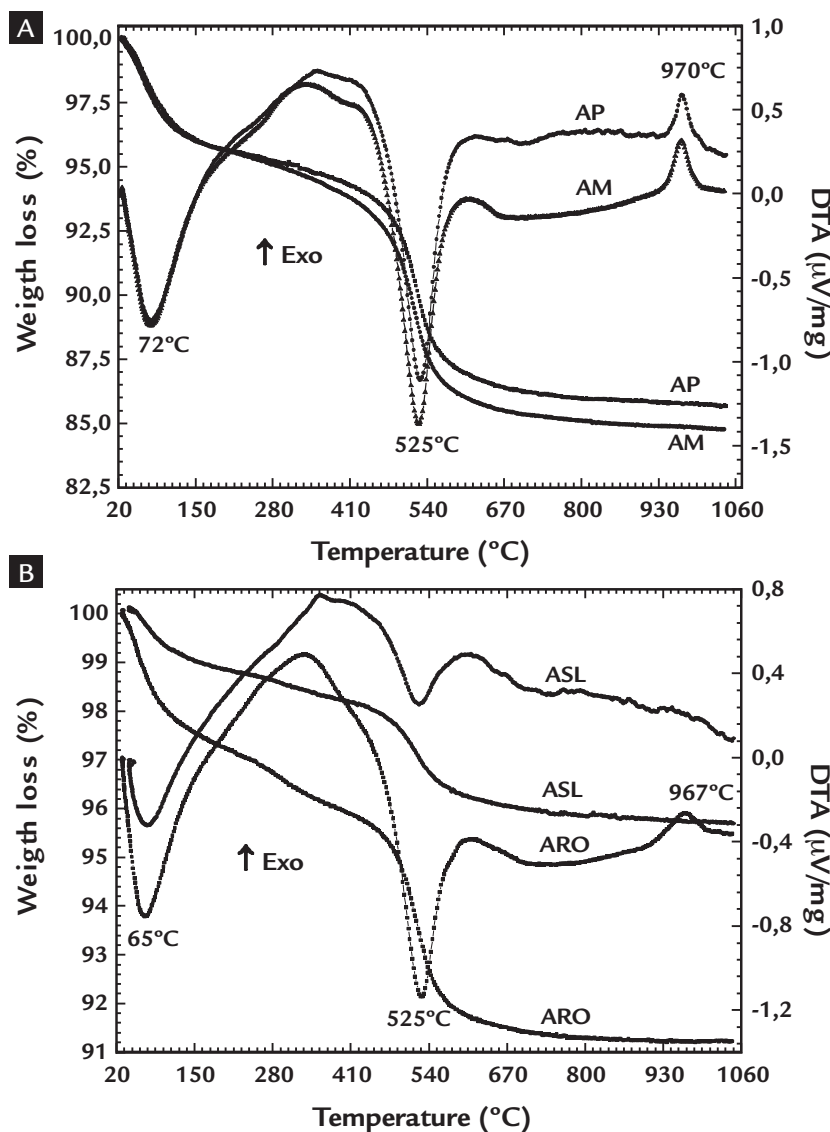


Figure 3
TG/DTA runs of the four clays:
A) AM and AP.
B) ARO and ASL.

Particle size distributions and Atterberg limits

Table 4 describes the granulometric analysis obtained by sieving and sedimentation.

Table 5 lists the Atterberg limits of the samples. Note that the liquid

limit (LL) varied from 44.70 to 57.60 %, the plastic limit (PL) from 27.41 to 30.26%, and the plasticity index (PI) ranged from 17.29 to 28.10%. These results allow us to state that these clays

have plasticity indices above 15%, and are considered highly plastic, according to the criteria of soil mechanics (Cardoso et al., 1998).

Technological Properties

Table 6 lists the technological properties of the clays in the temperature interval of 110-1250°C.

As can be seen, the flexural strength resistance (FSR) values of the AM and AP clays after drying at 110°C were 1.35 and

1.43 MPa, respectively. These values are lower than those reported in the literature (Bouger, 1995; Powell, 1996; Wilson,

Sample	Clay (%)	Silt (%)		Fine sand (%)
		Fine	Average	
AM	53.40	45.20	1.40	0.00
AP	52.20	30.20	17.60	0.00
ASL	34.30	43.64	1.64	20.42
ARO	22.60	30.00	12.82	34.58

Table 4
Particle size distribution
of the clays under study.

Clay= fraction < 2 μm ; Fine silt= fraction > 2 μm and < 6 μm ;
Average silt= fraction > 6 μm and < 20 μm ; Sand= fraction > 60 μm and < 200 μm

Determination	Sample			
	AM	AP	ASL	ARO
LL	56.85	57.60	44.70	49.50
PL	28.75	30.26	27.41	28.30
PI	28.10	27.34	17.29	21.20

Table 5
Atterberg limits
of the clays under study.

AM Clay				
T (° C)	Ls (%)	FSR (MPa)	WA (%)	Color
110	1.65 \pm 0.04	1.35 \pm 0.09	na *	Gray
850	3.14 \pm 0.25	3.70 \pm 0.35	32.67 \pm 1.29	Cream
950	5.14 \pm 0.44	4.20 \pm 0.40	31.44 \pm 1.29	Cream
1,050	6.21 \pm 0.27	7.00 \pm 0.56	27.46 \pm 0.04	Cream
1,150	13.07 \pm 0.29	24.20 \pm 1.20	9.81 \pm 1.62	Cream
1,250	15.11 \pm 0.30	32.58 \pm 1.20	1.93 \pm 0.05	Cream

AP Clay				
T (° C)	Ls (%)	FSR (MPa)	WA (%)	Color
110	1.45 \pm 0.03	1.43 \pm 0.06	na	Gray
850	2.90 \pm 0.30	7.14 \pm 0.13	26.66 \pm 2.75	White
950	4.35 \pm 0.01	9.84 \pm 0.30	24.43 \pm 2.20	White
1,050	5.88 \pm 0.14	14.64 \pm 1.29	23.13 \pm 2.00	White
1,150	13.11 \pm 0.01	32.79 \pm 2.00	10.14 \pm 1.23	Pale cream
1,250	16.29 \pm 0.08	36.66 \pm 7.23	2.34 \pm 0.17	Pale cream

ARO Clay				
T (° C)	Ls (%)	FSR (MPa)	WA (%)	Color
110	0.35 \pm 0.09	3.66 \pm 0.04	na	Brown
850	0.20 \pm 0.01	1.43 \pm 0.07	18.69 \pm 0.37	Red
950	0.26 \pm 0.05	2.15 \pm 0.11	17.72 \pm 0.14	Red
1,050	0.93 \pm 0.02	2.19 \pm 0.03	16.73 \pm 0.46	Red
1,150	2.36 \pm 0.06	4.13 \pm 0.06	14.28 \pm 0.23	Red
1,250	7.49 \pm 0.44	25.01 \pm 3.07	1.75 \pm 0.02	Dark brown

ASL Clay				
T (° C)	Ls (%)	FSR (MPa)	WA (%)	Color
110	0.20 \pm 0.07	3.33 \pm 0.02	na	Orange
850	0.15 \pm 0.03	1.28 \pm 0.03	15.91 \pm 1.00	Red
950	0.46 \pm 0.05	1.67 \pm 0.04	15.62 \pm 1.76	Red
1,050	0.25 \pm 0.06	1.86 \pm 0.01	14.51 \pm 1.13	Red
1,150	2.11 \pm 0.12	7.05 \pm 0.30	13.15 \pm 0.20	Red
1,250	4.69 \pm 0.65	23.39 \pm 1.73	0.71 \pm 0.09	Dark brown

Table 6
Ceramic properties
of the clays after firing.

* na = not available. FSR: Flexural strength resistance. WA: Water absorption. L_s: Linear shrinkage.

1998) for Brazilian and foreign ball clays, whose values vary from 4-10 MPa. The AM and AP clays show similar behavior upon firing, since their chemical and mineralogical compositions are identical. The WA of both samples decreases between 850-1250°C, indicating that their linear shrinkage increase (sintering). The FSR reached values of 30 MPa at 1250°C. These values are compatible with those of national reference clays used in ceramic whiteware. This finding is especially relevant because in Brazil high quality clays

for ceramic whiteware applications are not common, and most of them are located in the state of São Paulo (Motta, 1993; Cardoso et al., 1998).

The ASL and ARO clays present higher FSR values at 110°C than the AM and AP clays (3.33 MPa - ASL and 3.66 MPa - ARO), which is explained by their improved green packing and their corresponding granulometry (Table 4). The ASL and ARO clays heat-treated at 850°C present lower L_s values than the AM and AP samples. This is also due to the differ-

ence in granulometry (Table 2) and the high contents of non-plastic materials in their composition, which favor particle packing and reduce the thermal reactivity of ceramic bodies up to 1050°C. Between 1050°C and 1150°C, both clays undergo a similar increase in their L_s (\approx 2%), but at temperatures above 1150°C the ASL sample shows a higher sintering rate than ARO clay due to the presence of a larger amount of K₂O (Table 1), which acts as a fluxing agent, favoring the onset of the formation of liquid phase at temperatures

above 985°C, according to the $K_2O-Al_2O_3-SiO_2$ system (Levin et al., 1964).

Between 850 and 1050°C, the FSR

of ASL and ARO clays remains almost constant, reaching the highest value of 2 MPa. However, in the interval between

1150 and 1250°C, the FSR increases rapidly until it reach values exceeding 20 MPa.

4. Conclusions

Based on the results of this work, the samples under study can be divided into two groups: (i) Kaolinic clays that present high plasticity, containing small amounts of quartz and accessory minerals in their composition. These raw materials fire in shades of cream to white and, based on their ceramic properties (WA, FSR, S_T) in the firing interval applied here (850-1.250

°C), they can be classified as suitable for use in ceramic whiteware. (ii) Kaolinic clays containing hematite, quartz, feldspar (4% of K_2O), illite (ARO), small quantities of smectite (ASL) and of other accessory minerals in their composition, which can be used in red ceramics alone or together with others in the formulation of ceramic bodies. However, special attention should

be given to their use in the manufacture of ceramic materials due to the abundance of free silica in their compositions, which may cause an increase in the coefficient of thermal expansion of products, with the appearance of cracks during firing due to the polymorphic transition $\alpha \leftrightarrow \beta$ of cristobalite.

5. Acknowledgments

The authors gratefully acknowledge the Brazilian research funding agencies CAPES (PROCAD-AMAZÔNIA

through the project “Map of the Clays of the State of Maranhão: Registration of Occurrences and Mineralogical and Tech-

nological Characterization of Ceramic Raw Materials”) and FAPEMA for their financial support of this work.

6. References

- ANUÁRIO BRASILEIRO DE CERÂMICA. ASSOCIAÇÃO BRASILEIRA DE CERÂMICA (ABC), p. 76 (2002).
- ABNT- ASSOCIAÇÃO BRASILEIRA DE NORMAS TÉCNICAS. *NBR 6454:1984 - Determinação do limite de liquidez, método de ensaio*. Rio de Janeiro, 1984.
- _____. *NBR 7180:1984 - Determinação do limite de plasticidade, método de ensaio*. Rio de Janeiro, 1984.
- _____. *NBR 6457:1986 - Solo - análise granulométrica*. Rio de Janeiro, 1984.
- _____. *NBR 6457:1986 - Amostras de solo - preparação para ensaios de compactação e ensaios de caracterização*. Rio de Janeiro, 1986.
- _____. *NBR 6113:1997 - Materiais refratários densos conformados - determinação da resistência à flexão à temperatura ambiente*. Rio de Janeiro, 1997.
- _____. *NBR 6220:1997 - Materiais refratários densos conformados - determinação da densidade de massa aparente, porosidade aparente, absorção e densidade aparente da parte sólida*. Rio de Janeiro, 1997.
- BARBA, A. et al. *Materias Primas para la Fabricación de Soportes de Baldosas Cerámicas*. Castellón, España: AICE, 1997.
- BOUGER, A. K. Ball Clay. *Am. Ceram. Bull.*, v. 74, n. 6, p. 101-102, 1995.
- CARDOSO, S.R.F., SANTOS, H.S., COELHO A.V.C., SOUZA SANTOS P. Caracterização e propriedades cerâmicas de alguns caulins e argilas usados em cerâmica branca no Estado de São Paulo. *Cerâmica Industrial*, v. 4, n. 4-6, p. 39-47, 1998.
- _____. Caracterização e propriedades cerâmicas de alguns caulins e argilas usadas em cerâmica branca no Estado de São Paulo. *Cerâmica Industrial*. v. 3, n. 3, p. 47-57, 1998.
- COELHO, C., ROQUEIRO N., HOTZA D.. Rational mineralogical analysis of ceramics. *Material Letters*, v. 52, n. 6, p. 394-398, 2002.
- DIAZ RODRIGUEZ, A., TORRECILLAS A. Arcillas cerámicas: una revisión de sus distintos tipos, significados y aplicaciones. *Bol. Soc. Esp. Cerám. y Vidr.*, v. 41, n. 5, p. 459-470, 2002.
- EMILIANI G.P., CORBARA, F. *Tecnología Cerámica - Le Materia Prime*. Faenza, Itália: Gruppo Editoriale Faenza Editrice, 1999. p. 115
- FERREIRA, H.C., CHEN, T.P., ZANDONADI, A.R., SOUZA SANTOS, P. Correlações Lineares entre áreas específicas de caulins do Nordeste Brasileiro (Estados da Paraíba e Rio Grande do Norte). *Cerâmica*, v. 18, n. 71, p. 333-344, 1972.
- GARCIA VERDUCH, A. Origen y composición de las arcillas cerámicas. *Bol. Soc. Esp. Cerám. y Vidr.*, v. 24, n. 6, p. 396-404, 1985.

- CAPUTO, H. P. *Mecânica dos solos e suas aplicações fundamentais*. Rio de Janeiro: Livros Técnicos, 1994. v. 1.
- INSTITUTO BRASILEIRO DE GEOGRAFIA E ESTATÍSTICA (IBGE). Em: Contagem da população 2007. <http://www.ibge.gov.br/estadosat/perfil.php?sigla=ma>. Acessado em 10/2011.
- JOHNSON, L.J., CHU, C.H., HUSSEY G.A. Quantitative clay mineral analysis using simultaneous linear equations. *Clays and Clay Minerals*, v. 33, n. 2, p. 107-117, 1985.
- LEVIN, E.M., ROBBINS C. R., AND MCMURDIE H. F. Fig. 407 (p. 156, K₂O-Al₂O₃-SiO₂-SO₃) and Fig. 501 (p. 181, Na₂O-Al₂O₃-SiO₂) in *Phase Diagrams for Ceramists*. Edited by M. K. Reser. American Ceramic Society, Columbus, OH, 1964.
- MELLO, I.S.C., MOTTA, J.F.M., BEZERRA, M.S., NESI, J.R., LORETI JR, R. *Matérias-primas minerais cerâmicas do Nordeste Brasileiro*. São Paulo: CPRM, 184 p., 2011.
- MOTTA, J.F.M., TANNO L.C. e CABRAL Jr. M. argilas plásticas para cerâmica branca no Estado de São Paulo - potencialidade geológica. *Revista Brasileira de Geociências*, v. 23, n. 2, p 158-173, 1993.
- POWELL, P. S. Ball Clay Basics. *Am. Ceram. Bull.*, v. 75, n. 6, p. 74-76, 1996.
- SANTANA A. et al. *Cerâmica vermelha para construção: telhas, tijolos e tubos*. Série Mercado. In: Estudos de Mercado SEBRAE/ESPM, Setembro 2008. 95 p.
- SOUZA SANTOS, P. *Ciência e tecnologia das argilas*. 2. ed. São Paulo: Edgard Blucher, 1992. v. 1.
- THOREZ, J. *Phyllosilicates and clay minerals: a laboratory handbook for their x-ray diffraction analysis / Dison*. Belgium: Editions G. Lelotte, 1975. 579 p.
- VIEIRA COELHO A. C., SOUZA SANTOS P. Argilas especiais: o que são, caracterização e propriedades. *Química Nova*, v. 30, n. 1, p. 146-152, 2007.
- WILSON I. R. Constituição, avaliação e propriedades cerâmicas de “ball clays”. *Cerâmica*, v. 44, n. 287-288, p. 88-117, 1998.

Artigo recebido em 06 de março de 2012. Aprovado 27 em de junho de 2012.